

Contribution

Environmental-friendly Catalysts Learned from Vitamin B₁₂-Dependent Enzymes

Hisashi Shimakoshi and Yoshio Hisaeda

Department of Chemistry and Biochemistry, Graduate School of Engineering, Kyushu University,
Fukuoka 819-0395, Japan

1. Introduction

It is widely known that vitamin B₁₂ derivatives are unique coenzymes that possess cobalt-carbon (Co-C) bonds *in vivo* and are involved in a variety of catalytic functions in combination with various apoproteins.¹ Vitamin B₁₂ is a metal complex in which cobalt ions are coordinated to 4 ring nitrogen atoms in a corrin ring (**Figure 1**). It was originally developed as a magic bullet for the treatment of pernicious anemia, and its unique structure was elucidated by Hodgkin *et al.* by X-ray crystallography.² The oxidation state of the central cobalt ions range from

+1 to +3; Co(I) imparts a gray-green color, Co(II) imparts a yellow-to-orange color, and Co(III), which is the most common form, imparts a red color to the B₁₂ derivatives, and is known as the “red vitamin.” Methylcobalamin and adenosylcobalamin as the coenzyme forms are parts of *in vivo* enzymes that catalyze the biosynthesis of methionine and the isomerizations with carbon-skeleton rearrangements, respectively.³ Recent studies revealed that the complex of such corrin ring structures acts on the active center of the dechlorination reaction in anaerobic bacteria; this suggests a new function for the B₁₂-dependent enzymes (**Scheme 1**).⁴


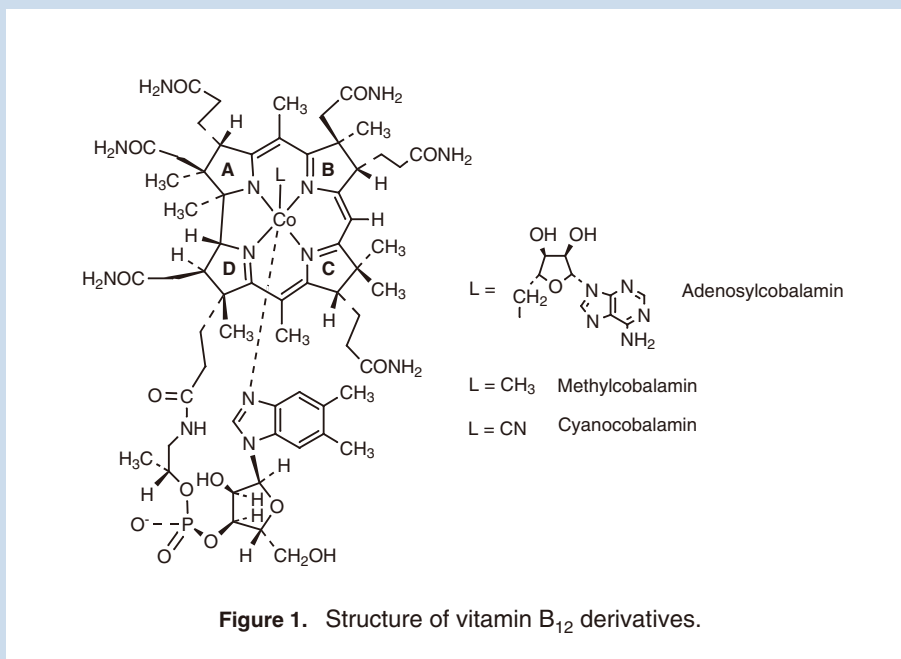



Figure 1. Structure of vitamin B₁₂ derivatives.

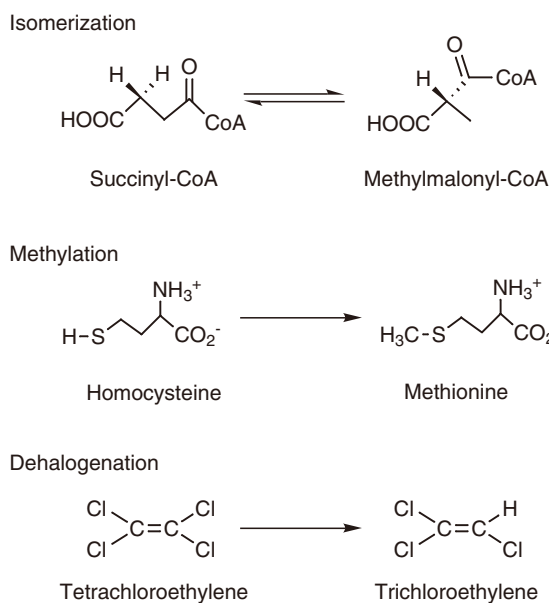

Scheme 1.

The most remarkable feature of the B_{12} -dependent enzyme reaction is the formation of a unique organometallic structure with a metal-carbon bond. This structure is mainly produced by the reactions of Co(I) with an organic halide and Co(III) with Grignard reagents, and it readily undergoes homolytic cleavage under mild exogenous stimuli such as visible light, heat, and redox treatment. Especially, when the former reaction occurs, formation of the Co–C bond involves dehalogenation of

the organic halide and produces organic radical species during cleavage of the Co–C bond (**Scheme 2**). By focusing on the above-mentioned features of the Co–C bond, we developed a molecular transformation utilizing the formation and cleavage of the Co–C bond with a B_{12} model complex that stimulates the active center of the B_{12} enzymes.⁵ In this article, we present our results on the synthesis of a vitamin B_{12} derivative and its catalytic application.

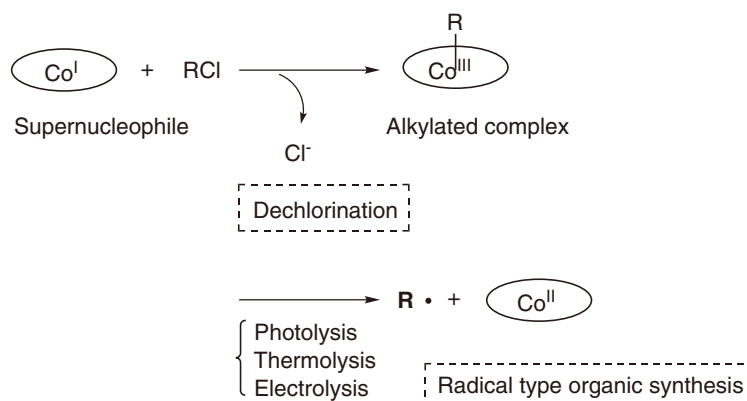

Scheme 2.

2. Modeling of vitamin B₁₂

Vitamin B₁₂ is obtained on a large scale from cyanocobalamin-producing organisms for use as dietary supplements or livestock feed. Thus far, no problems have occurred with regards to the safety or economics of using natural vitamin B₁₂ as a catalyst resource. However, natural vitamin B₁₂ supplied from bacteria contains many vitamin B₁₂-related substances, suggesting that it may have a poor chemical stability. This is not because of the instability of the corrin ring structure, but because of the deterioration of the side-chain substituents. As will be described later, the corrin ring structure has a high stability. To use the vitamin B₁₂ derivative as a catalyst, the following conditions should be satisfied: (1) the corrin ring structure should be retained, (2) the central cobalt atoms should be intact, and (3) the modifiable side-chains should be maintained. In light of these 3 conditions, we temporarily removed the physiologically essential side-

chain substituents from cyanocobalamin for synthesizing the hydrophobic vitamin B₁₂ (heptamethyl cobyrinate) by chemical modification of all the peripheral side-chains into ester groups (**Figure 2, Type A**).⁶ About 80% of the hydrophobic vitamin B₁₂ can be obtained using a single synthesis process by heating cyanocobalamin in alcohol in the presence of an acid catalyst, even when cyanocobalamin is used as the raw material, which is abundantly produced by microorganisms as mentioned above. Using the hydrophobic vitamin B₁₂ as a starting material, it is possible to synthesize various B₁₂ catalysts that can have wide applications (**Figure 2, Type B-D**). The corrin rings present in natural B₁₂ are retained in the above-mentioned complexes, and hence, the redox potential and electronic property of the central cobalt ion of the synthetic B₁₂ derivative are similar to those of natural B₁₂, suggesting that the synthetic B₁₂ derivative will show a high reactivity during molecular transformations like original enzymes.⁶

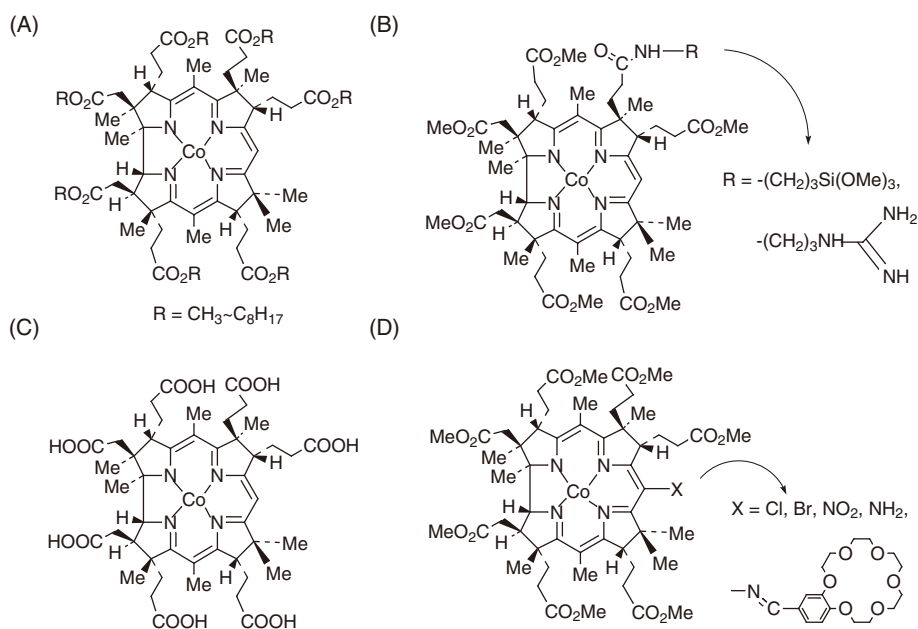


Figure 2. Modification of vitamin B₁₂ derivatives.

3. Electroorganic reaction using B₁₂ complex

As described above, nucleophilic Co(I) species of the B₁₂ derivative reacts with organic halides, which results in dehalogenation followed by the simultaneous production of an alkylated complex. Therefore, it may be important to develop a method to produce reactive Co(I) species to form the alkylated complex, which is a key intermediate of the B₁₂-dependent enzyme reaction. The synthesized B₁₂ complex can be reduced by chemical reductants, such as sodium borohydride, metallic zinc, and sodium amalgam, thus the mass use of these chemical reagents is not desirable in terms of synthetic as well as recent green chemistry. Consequently, an electrochemical technique

was used for generating Co(I) species of the B₁₂ complex, in which the B₁₂ complex works as a mediator for the electroorganic reaction (**Figure 3**).⁷

We developed various molecular transformations by controlled-potential electrolyses at the potentials of -1.4 or -1.5 V vs. Ag/AgCl using the hydrophobic vitamin B₁₂ as a mediator (**Scheme 3**). For example, when bromoalkyl acrylate was used as a substrate, large-membered ring lactones were synthesized by intramolecular cyclization of organic radical species generated by the homolytic cleavage of the alkylated complex (**Scheme 3, eq. 1**).⁸ The formation of the alkylated complex as the intermediate was directly observed by monitoring the electrolysis solution using electrospray ionization

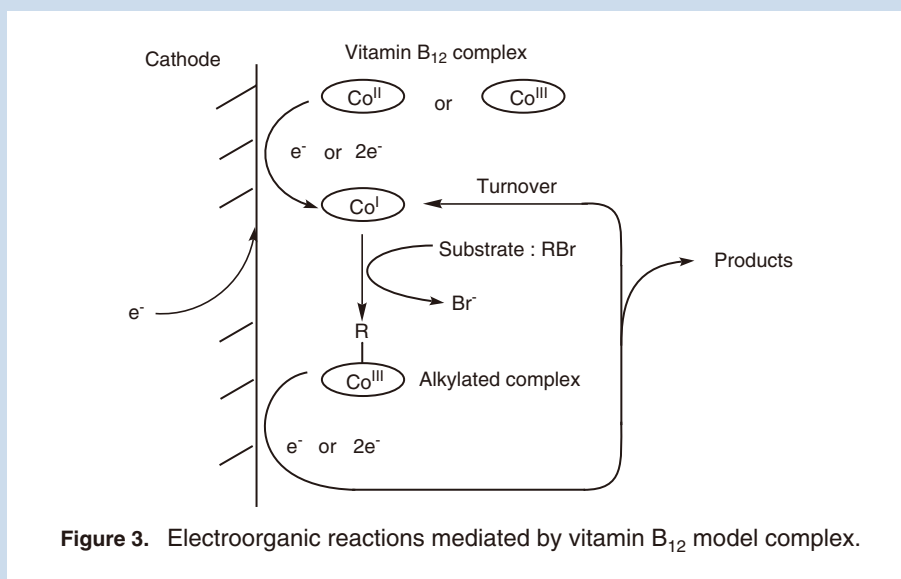
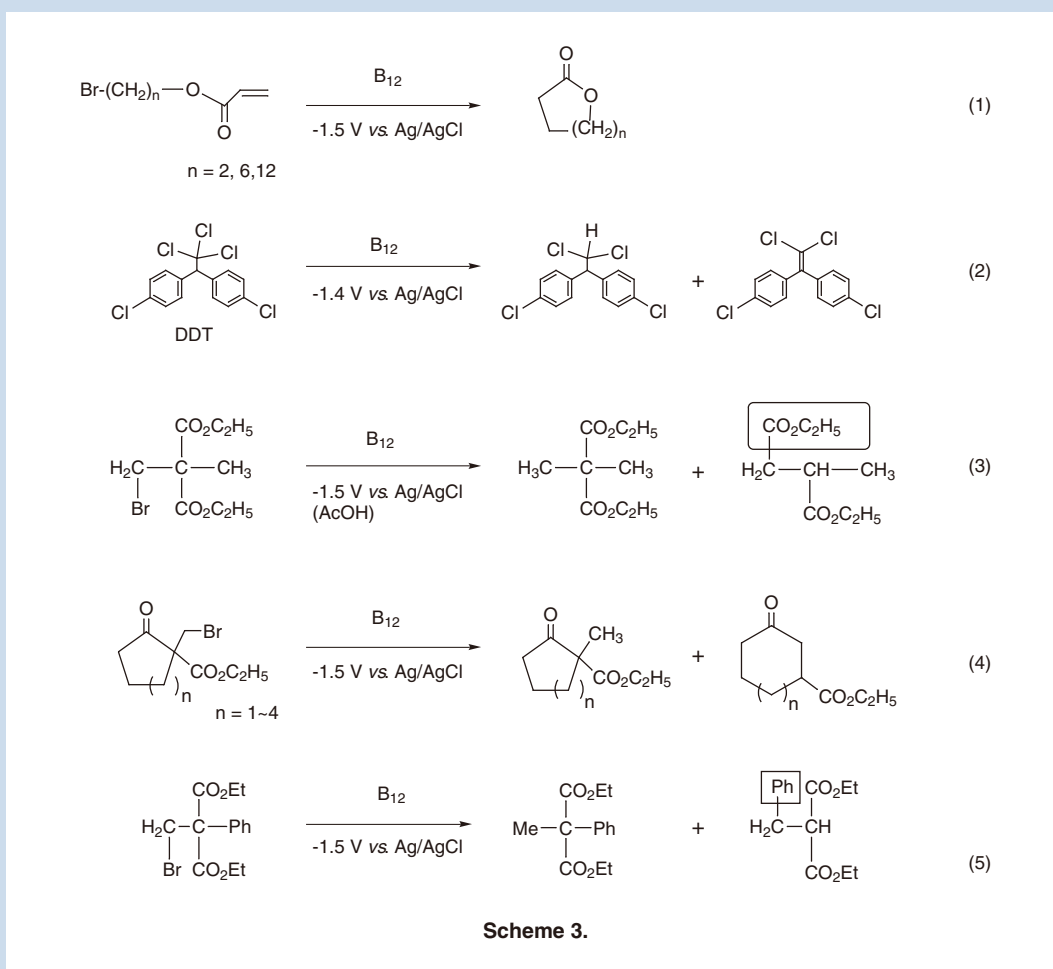


Figure 3. Electroorganic reactions mediated by vitamin B₁₂ model complex.

mass spectrometry (ESI-MS) and UV-vis spectra. The hydrophobic vitamin B₁₂ can also effectively act as a dechlorination catalyst of environmental pollutants, such as dichlorodiphenyltrichloroethane (DDT) (**Scheme 3, eq. 2**).⁹ It is noteworthy that the B₁₂ catalytic system does not generate toxic secondary pollutants such as chlorine gas and phosgene, because the chlorine atoms are dechlorinated to harmless chloride ions during the

reaction (**Scheme 2**). Furthermore, the B₁₂ catalyst was not degraded after the reactions. Its high durability was confirmed by UV-vis and mass spectrum analyses after the reaction. When other cobalt complexes, such as the porphyrin complex, were used under the same conditions, the complexes were severely degraded during the electrolysis.



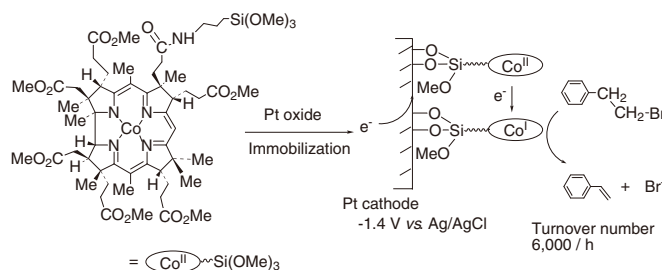


Figure 4. B₁₂ modified electrode for electroorganic reaction.

To utilize repeatedly such a robust B₁₂ catalyst, the B₁₂ complex was immobilized on the electrodes or dissolved in an ionic liquid for recovering or recycling after the reaction. In the former case, the B₁₂ complex could be immobilized on the platinum electrode surface at a coverage rate of approximately 1.6×10^{-10} mol/cm² by introducing a trimethoxysilyl group into the side-chain (**Figure 2, Type B**). The reactivity was evaluated using phenethyl bromide as the model substrate, which demonstrated a high catalytic activity with 6,000 turnover number per hour (**Figure 4**).¹⁰ After the reaction, the product and the B₁₂ catalyst could be easily separated as the B₁₂ catalyst was immobilized on the electrode. Other examples of the B₁₂-modified electrodes were also reported, such as a polymer-covered electrode, interface-polymerized electrode, and sol-gel film doped electrode.¹¹⁻¹³

On the other hand, when an ionic liquid was used as the reaction solvent, the B₁₂ complex was supported in an ionic liquid and showed the following various benefits. In general, an electroorganic reaction was carried out in a polar organic solvent containing supporting electrolytes. However, such a reaction using organic solvents containing many of the supporting electrolytes may not be desirable with regard to the recent regulated use of chemical reagents, even though this procedure is used to degrade chlorinated organic compounds. Recently, electroorganic reactions in an ionic liquid have been increasingly studied in order to address such issues. The ionic liquid is a room temperature liquid salt under ordinary pressure, which is characterized by its nonvolatility, fire retardance, and excellent electrical conductivity and is a superior solvent for the electroorganic reactions.¹⁴

When the electrolysis of DDT was carried out in an ionic liquid by using the B₁₂ complex as a catalyst, the reaction proceeded effectively in the same manner as the dechlorination reaction in the polar organic solvent containing supporting electrolytes. Furthermore, during the extraction process after the reaction, the product and B₁₂ complex could be separated in the organic solvent layer and the ionic liquid layer, respectively. The B₁₂ complex dissolved in an ionic liquid can be recycled for the reaction (**Figure 5**).¹⁵ More interestingly, the reactivity of the B₁₂ complex improved in the ionic liquid; i.e., the conversion efficiency of the substrate increased approximately 4-times that of the reaction performed in dimethylformamide (DMF). This enhanced reactivity in the ionic liquid over that in DMF could be explained by the application of the Hughes–Ingold predictions¹⁶ of solvent polarity effects on reaction rates. The reaction of electrochemically generated Co(I) with DDT is a “Menschutkin type of reaction” in which two neutral reactants, Co(I) and DDT, react to form charged products via a charge-separated activated complex in the polar ionic liquid, which ultimately decreases the activation energy, resulting in an increase in the reaction rate. A similar accelerating effect of the reaction in an ionic liquid has been closely examined by the reaction of methyl *p*-nitrobenzenesulfonate with tri-*n*-butylamine.¹⁷ Actually, the E_T^N value¹⁸ of the ionic liquid has been determined as a polarity index. For example, the value of 1-*n*-butyl-3-methylimidazolium tetrafluoroborate is 0.673, indicating it is highly polar compared to a polar organic solvent, such as DMF ($E_T^N = 0.386$).¹⁹

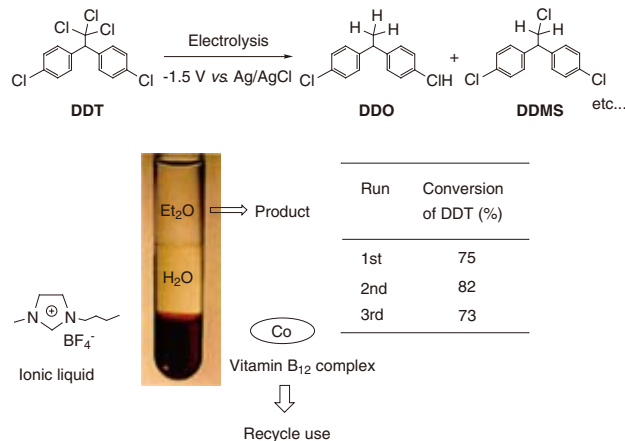


Figure 5. Reaction of vitamin B₁₂ complex in ionic liquid.

4. Photosensitized reaction of B₁₂ complex

We attempted to design a light-driven catalyzing system that could be used for the development of a clean molecular transformation using the B₁₂ complex. Light is one of the abundant and cleanest energies on the earth and has been used in organic syntheses for a long time. Thus, we focused on a ruthenium(II) tris bipyridine complex ([Ru^{II}(bpy)₃]Cl₂), which has been widely used as a photosensitizer, and constructed the catalyzing system using a photo-induced electron transfer reaction for producing Co(I) species.²⁰ The [Ru^{II}(bpy)₃]Cl₂ complex was excited under visible light irradiation and the [Ru(bpy)₃]⁺ complex with high reduction potential (−1.35 V vs. Ag/AgCl) was produced due to reductive quenching by a sacrificial electron donor such as triethanolamine.²¹ Therefore, it is possible to generate the catalytically active B₁₂ complex ($E_{1/2}(\text{Co}^{\text{II}}/\text{Co}^{\text{I}}) = -0.6 \text{ V vs. Ag/AgCl}$)

by electron transfer from the ruthenium photosensitizer. Based on this strategy as shown in **Figure 6**, the dechlorination of DDT was carried out using the B₁₂ complex in the presence of the ruthenium photosensitizer and sacrificial electron donor. Consequently, most of the DDT was converted to DDD, a mono-dechlorination product, within 3 hours. The reaction was hardly facilitated in the absence of the B₁₂ complex or in the dark. Therefore, it is suggested that Co(I), which is produced by a photo-induced electron transfer reaction, might act as an active species to initiate the reaction. The ESR spectral change confirmed that the electron transfer reaction of the ruthenium photosensitizer reduces the B₁₂ complex to Co(I) species. Characteristic ESR signals were detected for the paramagnetic Co(II) of B₁₂, while the corresponding ESR signals for diamagnetic Co(I) were absent in the photoreaction (**Figure 7**).

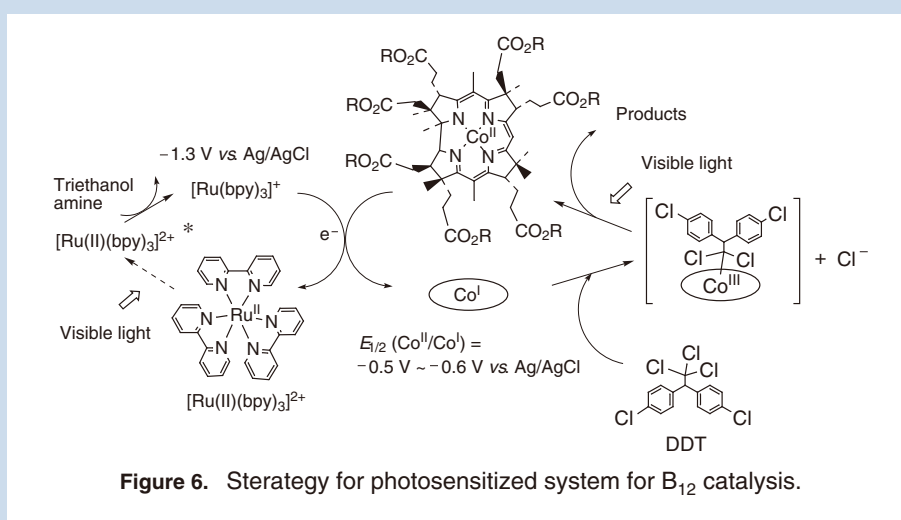


Figure 6. Strategy for photosensitized system for B₁₂ catalysis.

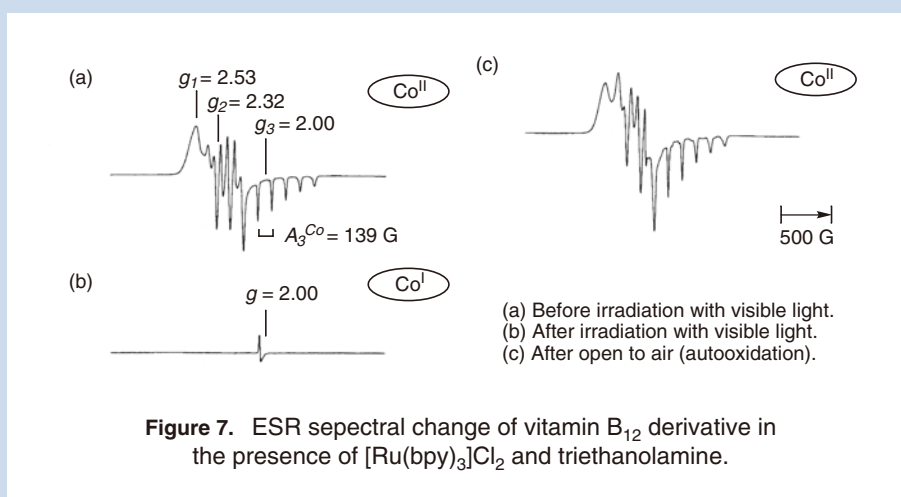


Figure 7. ESR spectral change of vitamin B₁₂ derivative in the presence of [Ru(bpy)₃]Cl₂ and triethanolamine.

5. B₁₂-TiO₂ hybrid catalyst

Recently, hybrid catalysts composed of a metal complex and various semiconductors with photosensitizing ability have been reported.^{22,23} According to this technique, it is possible to develop a hybrid catalyst with concerted

effects of metal complexes and semiconductors. Thus, we focused on titanium oxide,²⁴ which is an n-type semiconductor, to develop a light energy driven B₁₂-TiO₂ hybrid catalyst. The reduction power of the excited electrons in the titanium oxide (TiO₂)-conduction band (−0.5 V vs. normal hydrogen electrode (NHE))²⁵ enabled

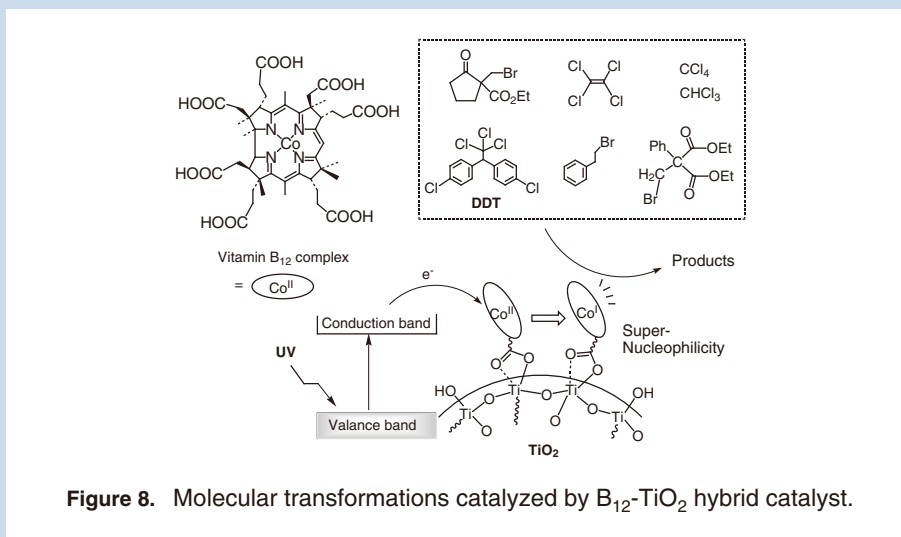


Figure 8. Molecular transformations catalyzed by B₁₂-TiO₂ hybrid catalyst.

the reduction of the B₁₂ complex to the catalytically active Co(I) species, and this indicated that a light energy-driven hybrid catalyst can be developed by immobilizing the B₁₂ complex on TiO₂. In this case, TiO₂ not only played a role as a scaffold for the B₁₂ complex, but also served as an electron source for the reduction of the B₁₂ complex (**Figure 8**). Here, the B₁₂ complex was immobilized on TiO₂ by multiple interactions of the carboxyl groups of B₁₂ (**Figure 2, Type C**) and surface hydroxyl groups of TiO₂. Approximately 3–4 × 10⁻⁵ mol (40–50 mg) of the B₁₂ complex (cobyrinic acid) was found to immobilize on 1 g of TiO₂ and 70–80% of the TiO₂ surface was covered with the B₁₂ complex. The resulting B₁₂ complex was firmly immobilized on the TiO₂ surface, and the immobilization remained stable for more than 1 year even after being dispersed in various organic solvents, such as an alcohol, and was not separated by ultrasonic treatment.

When a degradation reaction of a chlorinated organic compound, such as DDT, is performed using this hybrid catalyst, only a few milligrams of the catalyst can dechlorinate 100 times that of DDT in approximately 1 day.²⁶ The hybrid catalyst was activated by light energy so that neither chemical reagents nor expensive reactors are required. Ultraviolet irradiation provided by black light (365 nm) is sufficient for the photoexcitation

of TiO₂. Furthermore, both the B₁₂ complex and TiO₂ are non-toxic, thus the B₁₂-TiO₂ hybrid catalyst may be an environmental/human friendly catalyst. In addition, we investigated the use of the hybrid catalyst in radical reactions for organic synthesis. This result indicated that this hybrid catalyst could be applied to various molecular transformations, including the above-mentioned ring expansion reactions (**Scheme 3, eq. 4**) and 1,2-migration of the functional group (**Scheme 3, eq. 5**). Thus, the hybrid catalyst can be used as an alternative for the conventional radical organic synthetic reagent that uses a tin compound (Bu₃SnH/AIBN system).

TiO₂ can also be immobilized on carriers, such as glass substrates and beads, when it is converted to slurry sol solutions. Thin films of TiO₂ (with a thickness of a few hundred nanometers), which are prepared on glass substrates by dip-coating, can be hybridized with the B₁₂ complex by only dipping into the B₁₂ complex solution containing carboxyl groups. Thus the prepared B₁₂-TiO₂ hybrid catalyst on a glass plate also catalyzed the above-mentioned reactions (**Figure 9**). The immobilization of the B₁₂-TiO₂ hybrid catalyst on a glass plate can simplify the reaction process, and furthermore, facilitate the separation procedure of the product from the reaction mixture.


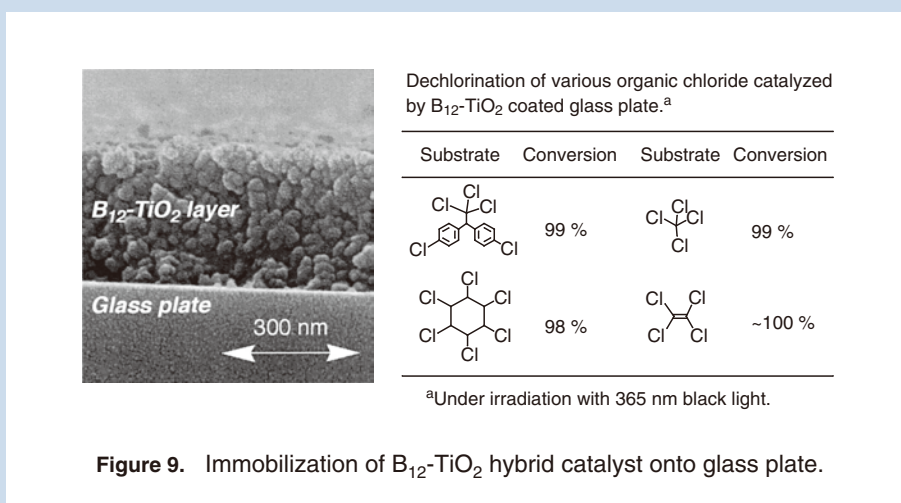


Figure 9. Immobilization of B₁₂-TiO₂ hybrid catalyst onto glass plate.

6. Vitamin B₁₂-hyperbranched polymer hybrid catalyst

A hyperbranched polymer is one of the dendric polymers that are synthesized via a one-step polymerization reaction in an inexpensive and easy way, and it has various advantages when compared to dendrimers, which are synthesized via multiple-step polymerizations.²⁷ Furthermore, as the polymer has a higher solubility and lower solution viscosity compared to linear polymers, it is expected to be used in a homogeneous solution.²⁸ In fact, the hyperbranched polymers that have many terminal functional groups due to their highly branched structure are appropriate for carrying functionalized

molecules.²⁹ Considering the nanospace provided by the hyperbranched polymers as a new catalyst reaction field, the B₁₂-hyperbranched polymer hybrid catalyst was synthesized (**Scheme 4**).³⁰ The amount of B₁₂ complex used can be adjusted to somewhere between a few % and 70% per terminal functional groups of the hyperbranched polymers, and the density of the B₁₂ complex can be readily controlled. When the B₁₂ complex is densely immobilized, a cooperative effect of the adjacent complex facilitates the dimerization reaction of phenethyl bromide.³¹ It is expected that the variable size and main chain polymer of the hyperbranched polymer will be able to produce various reaction characteristics.

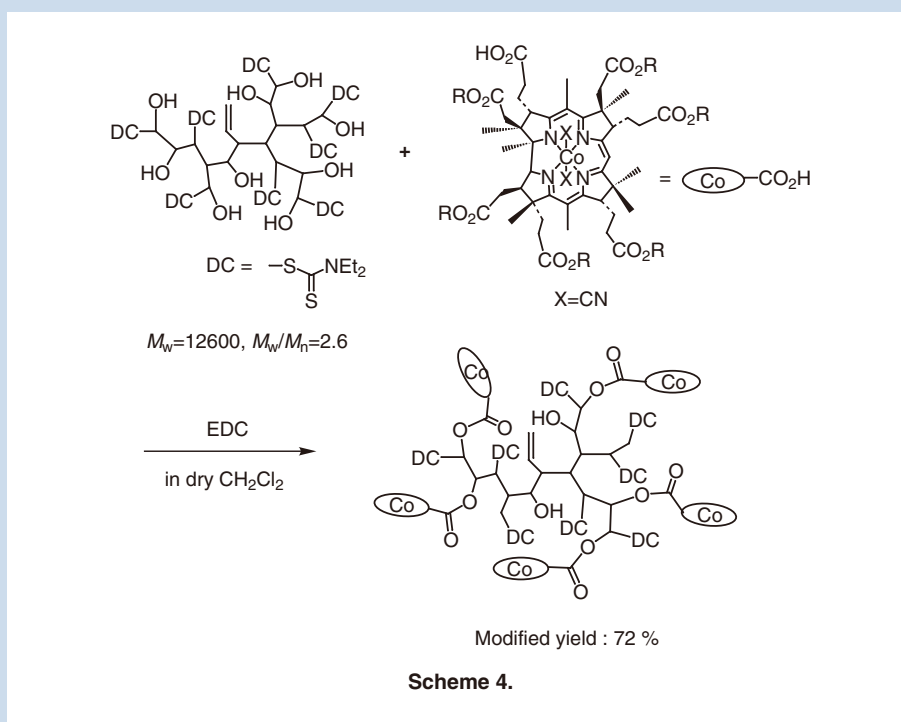

7. Conclusions

We have outlined the development of molecular transformations learned from the B₁₂-dependent enzymes. The hybrid catalyst composed of synthesizing metal complexes, which are similar to the active center of the B₁₂ enzyme, enabled various molecular transformations including environmentally-friendly organic synthesis reactions and degradation reactions of organic halides pollutants by an electroorganic reaction or a photochemical reaction. Combining the benefits of natural enzymes and engineering methods will allow the development of a new catalyst system that will exceed biological reactions. The

development of this bio-inspired chemistry introduced by us will play an important role in the next generation's science and technology.

Acknowledgments - This work was partially supported by a Grant-in-Aid for Scientific Research on Priority Areas (452 and 460) and Global COE Program "Science for Future Molecular Systems" from the Ministry of Education, Culture, Sports, Science and Technology (MEXT) of Japan, and an Industrial Technology Research Grant Program in 2005 from New Energy and Industrial Technology Development Organization (NEDO) of Japan.

References

- (a) *Vitamin B₁₂ and B₁₂-Proteins* ed. by B. Kräutler, D. Arigoni, B. T. Golding, Wiley-VCH **1998**; (b) *Chemistry and Biochemistry of B₁₂* ed. by R. Banerjee, Wiley-Interscience **1999**.
- (a) D. C. Hodgkin, J. Pickworth, J. H. Robertson, K. N. Trueblood, R. J. Prosen, J. G. White, *Nature* **1955**, *176*, 325-328; (b) D. C. Hodgkin, J. Kamper, M. Mackay, J. Pickworth, K. N. Trueblood, J. G. White, *Nature* **1956**, *178*, 64-66; (c) P. G. Lenhert and D. C. Hodgkin, *Nature* **1961**, *192*, 937-938.
- (a) R. Banerjee and S. W. Ragsdale, *Annu. Rev. Biochem.* **2003**, *72*, 209-247; (b) T. Toraya, *Chem. Rev.* **2003**, *103*, 2095-2127; (c) B. Kräutler, *Biochem. Soc. Trans.* **2005**, *33*, 806-810.
- (a) G. Glod, U. Brodmann, W. Angst, C. Holliger, R. P. Schwarzenbach, *Environ. Sci. Technol.* **1997**, *31*, 3154-3160; (b) C. Holliger, G. Wohlfarth, G. Diekert, *FEMS Microbiol. Rev.* **1999**, *22*, 383-398; (c) B. Kräutler, W. Fieber, S. Ostermann, M. Fasching, K. -H. Ongania, K. Gruber, C. Kratky, C. Mikl, A. Siebert, G. Diekert, *Helv. Chim. Acta* **2003**, *86*, 3698-3716; (d) S. Ruppe, A. Neumann, G. Diekert, W. Vetter, *Environ. Sci. Technol.* **2004**, *38*, 3063-3067; (e) K. M. McCauley, D. A. Pratt, S. R. Wilson, J. Shey, T. J. Burkey, W. A. van der Donk, *J. Am. Chem. Soc.* **2005**, *127*, 1126-1136; (f) J. E. Argüello, C. Costentin, S. Griveau, J. -M. Sáveant, *J. Am. Chem. Soc.* **2005**, *127*, 5049-5055.
- Reviews: (a) Y. Hisaeda, T. Nishioka, Y. Inoue, K. Asada, T. Hayashi, *Coord. Chem. Rev.* **2000**, *198*, 21-25; (b) K. L. Brown, *Chem. Rev.* **2005**, *105*, 2075-2150.
- (a) Y. Murakami, Y. Hisaeda, A. Kajihara, *Bull. Chem. Soc. Jpn.* **1983**, *56*, 3642-3646; (b) Y. Murakami, Y. Hisaeda, A. Kajihara, T. Ohno, *Bull. Chem. Soc. Jpn.* **1984**, *57*, 405-411.
- R. Scheffold, G. Rytz, L. Walder, *Modern Synthetic Methods*, Vol. 3, ed. By R. Scheffold, John Wiley & Sons, **1983**, 355-440.
- H. Shimakoshi, A. Nakazato, T. Hayashi, Y. Tachi, Y. Naruta, Y. Hisaeda, *J. Electroanal. Chem.* **2001**, *507*, 170-176.
- (a) H. Shimakoshi, M. Tokunaga, Y. Hisaeda, *Dalton Trans.* **2004**, 878-882; (b) H. Shimakoshi, Y. Maeyama, T. Kaieda, T. Matsuo, E. Matsui, Y. Naruta, Y. Hisaeda, *Bull. Chem. Soc. Jpn.* **2005**, *78*, 859-863.
- H. Shimakoshi, M. Tokunaga, K. Kuroiwa, K. Kimizuka, Y. Hisaeda, *Chem. Commun.* **2004**, 50-51.
- (a) A. Ruhe, L. Walder, R. Scheffold, *Helv. Chim. Acta* **1985**, *68*, 1301-1311; (b) Y. Murakami, Y. Hisaeda, T. Ozaki, Y. Matsuda, *J. Chem. Soc., Chem. Commun.* **1989**, 1094-1096; (c) D.-L. Zhou, C. K. Njue, J. F. Rusling, *J. Am. Chem. Soc.* **1999**, *121*, 2909-2914; (d) C. K. Njue and J. F. Rusling, *Electrochem. Commun.* **2002**, *4*, 340-343.
- R. Fraga, J. P. Correia, R. Keese, L. M. Abrantes, *Electrochim. Acta* **2005**, *50*, 1653-1655.
- H. Shimakoshi, A. Nakazato, M. Tokunaga, K. Katagiri, K. Ariga, J. Kikuchi, Y. Hisaeda, *Dalton Trans.* **2003**, 2308-2312.
- T. Welton, *Chem. Rev.* **1999**, *99*, 2071-2083.
- M. Jabbar, H. Shimakoshi, Y. Hisaeda, *Chem. Commun.* **2007**, 1653-1654.
- K. A. Cooper, M. L. Dhar, E. D. Hughes, C. K. Ingold, B. J. MacNulty, L. I. Woolf, *J. Chem. Soc.* **1948**, 2043-2046.
- L. Crowhurst, N. L. Lancaster, J. M. P. Arlandis, T. Welton, *J. Am. Chem. Soc.* **2004**, *126*, 11549-11555.
- C. Reichardt, *Solvent and Solvent Effects in Organic Chemistry*, VCH (UK) Ltd., Cambridge, UK, 2nd edn, **1998**.
- (a) S. N. V. K. Aki, J. F. Brennecke, A. Samanta, *Chem. Commun.* **2001**, 413-414; (b) M. J. Muldoon, C. M. Gordon, I. R. Dunkin, *J. Chem. Soc., Perkin Trans. 2*, **2001**, 433-435.
- (a) H. Shimakoshi, M. Tokunaga, T. Baba, Y. Hisaeda, *Chem. Commun.* **2004**, 1806-1807; (b) H. Shimakoshi, S. Kudo, Y. Hisaeda, *Chem. Lett.* **2005**, *34*, 1806-1807.
- A. Juris, V. Balzani, F. Barigelletti, S. Campagna, P. Belser, A. V. Zelewsky, *Coord. Chem. Rev.* **1988**, *84*, 85-277.
- (a) S. O. Obare, T. Ito, G. J. Meyer, *Environ. Sci. Technol.* **2005**, *39*, 6266-6272; (b) Y. Astuti, E. Palomarse, S. A. Haque, J. R. Durrant, *J. Am. Chem. Soc.* **2005**, *127*, 15120-15126; (c) S. O. Obare, T. Ito, G. J. Meyer, *J. Am. Chem. Soc.* **2006**, *128*, 712-713; (d) B. I. Ipe and C. M. Niemeyer, *Angew. Chem. Int. Ed. Engl.* **2006**, *45*, 504-507.
- R. J. Kuhler, G. A. Santo, T. R. Caudill, E. A. Betterton, R. G. Arnold, *Environ. Sci. Technol.* **1993**, *27*, 2104-2111.
- (a) M. A. Fox, *Acc. Chem. Res.* **1983**, *16*, 314-321; (b) M. D. Ward, J. R. White, A. J. Bard, *J. Am. Chem. Soc.* **1983**, *105*, 27-31; (c) M. A. Fox and M. T. Dulay, *Chem. Rev.* **1993**, *93*, 341-357; (d) M. R. Hoffmann, S. T. Martin, W. Choi, D. W. Bahnemann, *Chem. Rev.* **1995**, *95*, 69-96.
- A. Fujishima, T. N. Rao, D. A. Tryk, *J. Photochem. Photobiol. C: Photochem. Rev.* **2000**, *1*, 1-21.
- H. Shimakoshi, E. Sakumori, K. Kaneko, Y. Hisaeda, *Chem. Lett.* **2009**, *38*, 468-469.
- M. Jikei and M. Kakimoto, *Prog. Polym. Sci.* **2001**, *26*, 1233-1285.
- P. H. Toy and K. D. Janda, *Acc. Chem. Res.* **2000**, *33*, 546-554.
- (a) K. Ishizu and A. Mori, *Polym. Int.* **2001**, *50*, 906-910; (b) K. Ishizu, T. Shibuya, A. Mori, *Polym. Int.* **2002**, *51*, 424-428; (c) K. Ishizu, T. Shibuya, J. Park, S. Uchida, *Polym. Int.* **2004**, *53*, 259-265.
- K. Tahara, H. Shimakoshi, A. Tanaka, Y. Hisaeda, *Tetrahedron Lett.* **2007**, *48*, 5065-5068.
- K. Tahara, H. Shimakoshi, A. Tanaka, Y. Hisaeda, unpublished result.

(Received Jul. 2009)

Introduction of the authors

Hisashi Shimakoshi

Assistant Professor, Graduate School of Engineering, Kyushu University

Education:

B. S. and M. S., Doshisha University

Ph. D., Kyushu University

Professional Experiences:

1996-present Assistant Professor, Kyushu University

Honors:

2002 Synthetic Organic Chemistry Award for Young Scientists in Kyushu-Yamaguchi

2004 Electroorganic Chemistry Award for Young Scientists

Expertise and Speciality:

Coordination chemistry, Bioinorganic chemistry

Yoshio Hisaeda

Professor, Graduate School of Engineering, Kyushu University

Education:

B. S., M. S., and Ph. D., Kyushu University

Professional Experiences:

1981-1988 Research Associate, Kyushu University

1988-1995 Associate Professor, Kyushu University

1993-1994 Visiting Professor, The University of Texas at Austin

1995-present Professor, Kyushu University

Honors:

1991 The Chemical Society of Japan Award for Young Chemists (The 40th Shinpo-sho)

2008 BCSJ Award Article

Expertise and Speciality:

Biofunctional chemistry, Coordination chemistry, and Electroorganic chemistry

TCI Related Compound

Cyanocobalmin (vitamin B₁₂)
100mg, 1g [C0449]

